

Towards mapping the 3D-modulated spin texture of skyrmions in thin helimagnets

Schneider, S.^{1,2}, Wolf, D.³, Stolt, M.J.⁴, Jin, S.⁴, Pohl, D.^{3,5}, Rellinghaus, B.^{3,5}, Schmidt, M.⁶, Büchner, B.³, Goennenwein, S.T.B.⁵, Nielsch, K.^{3,5} and Lubk, A.³

¹ IFW Dresden, Germany, ² TU Dresden, Germany, ³ IFW Dresden, Germany, ⁴ University of Wisconsin-Madison, United States, ⁵ TU Dresden, Germany, ⁶ Max Planck Institute for Chemical Physics of Solids, Germany

Skyrmions [1] are topologically non-trivial vortex-like spin textures, anticipated for application in spintronic technologies, in next generation magnetic data processing and storage due to their facile manipulation by spin-polarized currents of very low magnitude [2, 3]. Unfortunately, little is known about the 3D structure of skyrmions [4, 5], ubiquitous in thin film technology. Here, we bridge that gap by combining the concept of the transport of intensity equation (TIE) [6], focal series in-line electron holography (EH), and off-axis EH [7] to quantitatively reconstruct the projected magnetic field pertaining to both the helical and the skyrmion lattice phase in single crystal nanoparticles of the isotropic chiral magnet $\text{Fe}_{0.95}\text{Co}_{0.05}\text{Ge}$.

The skyrmion phase in $\text{Fe}_{0.95}\text{Co}_{0.05}\text{Ge}$ particles (Fig. 1 (b)) was investigated using a double corrected FEI Titan 80-300 microscope operated in image corrected Lorentz mode. A focal series of Lorentz TEM (L-TEM) images of a single isolated nanoplatelet oriented along the [001] zone axis (Fig. 1 (a)) was recorded. Reconstruction of the phase of the electron wave and thereby of the magnetic induction was obtained with the help of a modified Gerchberg-Saxton type algorithm. To supplement the focal series reconstructions from large field of views, smaller areas of the identical nanoplatelet were investigated by off-axis EH. A direct tomographic investigation of the 3D structure of the skyrmionic lattice is currently experimentally unfeasible, because this would require an externally applied out-of-plane magnetic field to be tilted with the sample.

Thus, indirect experimental evidence for the 3D structure of the skyrmionic lattice may currently only be inferred from a quantitative analysis of the projected magnetic induction in the sample conducted with the help of EH. Fig. 2 (a) depicts an underfocused L-TEM micrograph showing the hexagonal that reveals the skyrmion lattice. The image is one out of 21 of the focal series used for an in-line holography reconstruction of the object exit wave in amplitude and phase. Figs. 2 (b, c) show magnetic induction maps $\bar{B}_\perp(x, y)$ in cylindrical coordinate representation visualizing the spin texture of the skyrmions by $\bar{B}_\phi(x, y)$ (Fig. 2(b)) and their donut-shaped magnitude by $\bar{B}_r(x, y)$ (Fig. 2 (c)). Likewise, we observed magnetic induction maps (Figs. 2 (e, f)) from a phase image reconstructed by off-axis EH (Fig. 2(d)) on the same $\text{Fe}_{0.95}\text{Co}_{0.05}\text{Ge}$ nanoplatelet. Most strikingly, we consistently observe a reduction of the projected in-plane \mathbf{B} -fields ($\bar{B}_{\max} = (0.2 \dots 0.3) T$) as compared to those of a homogeneous skyrmion throughout the film thickness. Two alternative models for the 3D structure of skyrmions are thus derived.

[1] A. N. Bogdanov and A. Hubert, *Journal of Magnetism and Magnetic Materials* 138, 255 (1994).

[2] N. Nagaosa and Y. Tokura, *Nature Nanotechnology* 8, 899 (2013).

[3] N. Kanazawa et al., "Noncentrosymmetric Magnets Hosting Magnetic Skyrmions" (2017).

[4] F. N. Rybakov et al., *Physical Review B - Condensed Matter and Materials Physics* 87, 094424 (2013).

[5] H. S. Park et al., *Nature Nanotechnology* 9, 337 (2014).

[6] A. Lubk et al., *Physical Review Letters* 111, 173902 (2013).

[7] H. Lichte et al., *Ultramicroscopy* 134, 126 (2013).

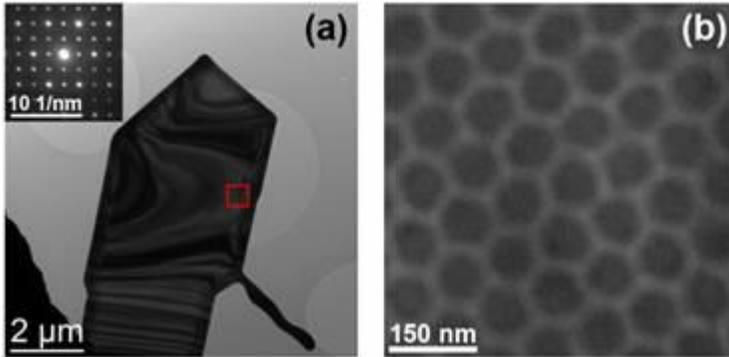


Fig. 1: (a) TEM image of a Fe_{0.95}Co_{0.05}Ge nanoplatelet in [001] with the diffraction pattern in the inset. (b) Skyrmion lattice as observed within the marked area in panel (a).

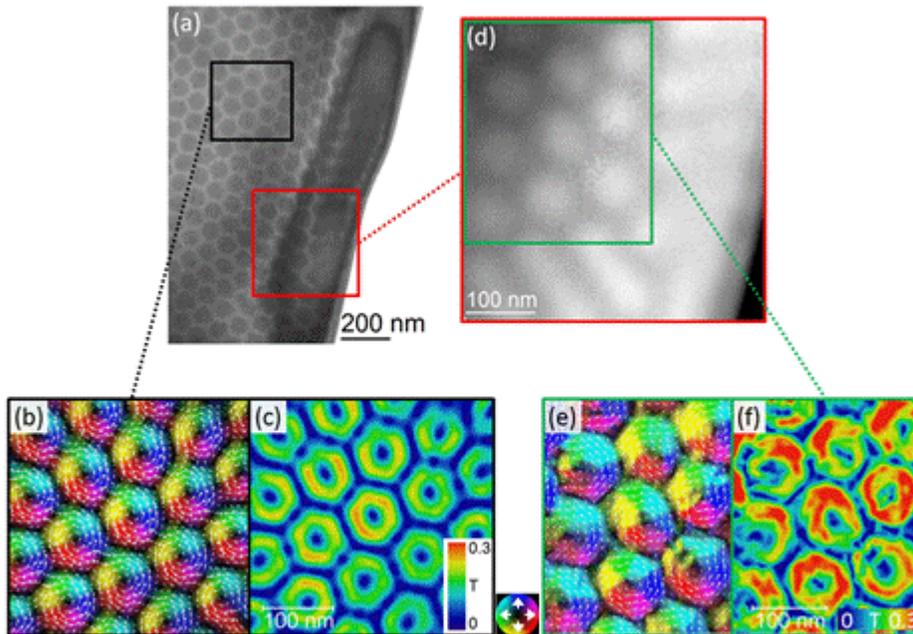


Fig. 2: (a) L-TEM image in under-focus showing the skyrmions as dark contrast. (d) Phase image of the position indicated by the red square in (a). (b, e) Mapping of the direction of the in-plane magnetic flux by combining a vector plot (white arrows) and a false color image. (c, f) False colour mapping of the magnitude of the in-plane magnetic flux.